

# Identifying the Crystalline Orientation of BP

by Guo Shuaifei  
Zhang Zhongyu  
Zhang Yu

# Purpose of the project

As a layered material, BP has a great anisotropic nature because of its structure (figure 1). Our final purpose is to find the electronic property of a BP device under stretching or compressing (figure 2). While the first step is to identify the crystal orientation of few layer BP.

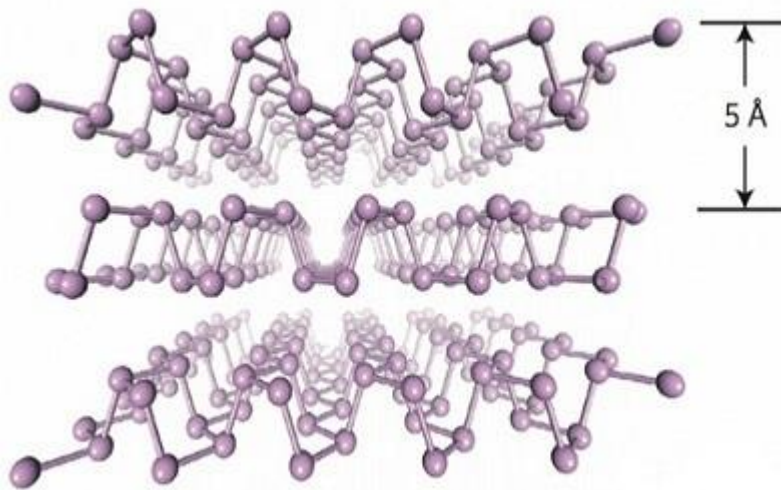


Figure 1. structure of few-layer BP  
Li *et al.*

<页脚>



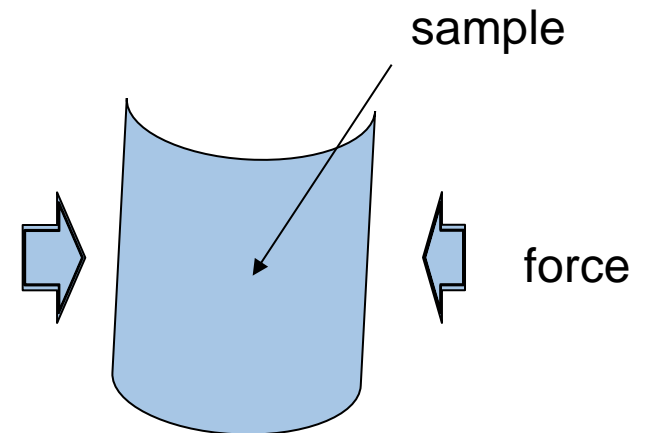


figure 2. our experiment configuration

# I. Utilizing the angle resolve Raman spectrum

# Raman peaks of black phosphorus

- Among the many ways to identify the crystal orientation the optical method is quick, easy and nondestructive.
- One can observe 3 typical Raman peaks, that is,  $A_g^1$  at 363  $\text{cm}^{-1}$ ,  $B_{2g}$  at 440  $\text{cm}^{-1}$ , and  $A_g^2$  at 467  $\text{cm}^{-1}$ . And the corresponding vibration modes are as follows:

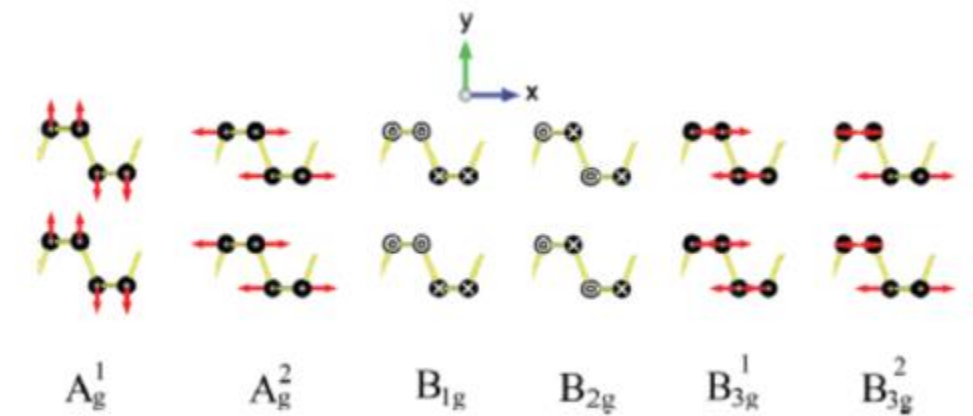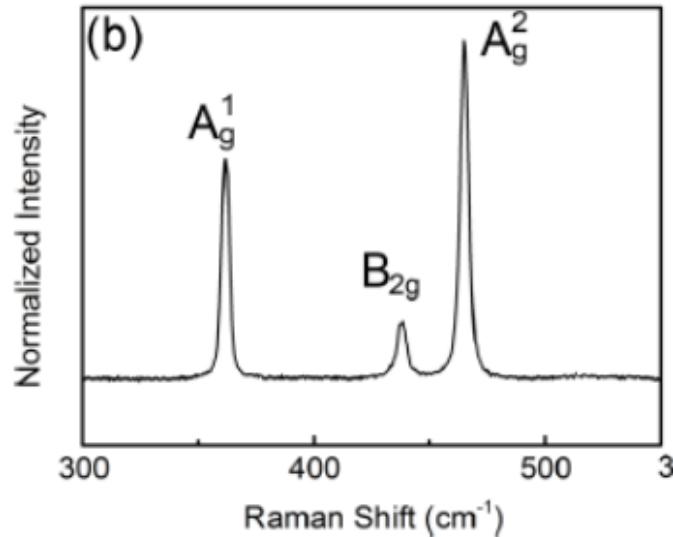

<页脚>

figure3.BP Raman spectrum

figure4. vibration modes

# Device setup -- first generation

Method I : using one quarter wave plate and two polarizers to creat a polarized light with constant light intensity and changable polarization direction. (Figure 5) In this configuration we can only measure the parallel component of the scattered light.

Failed – Difficulties in producing and maintaining circular polarized light

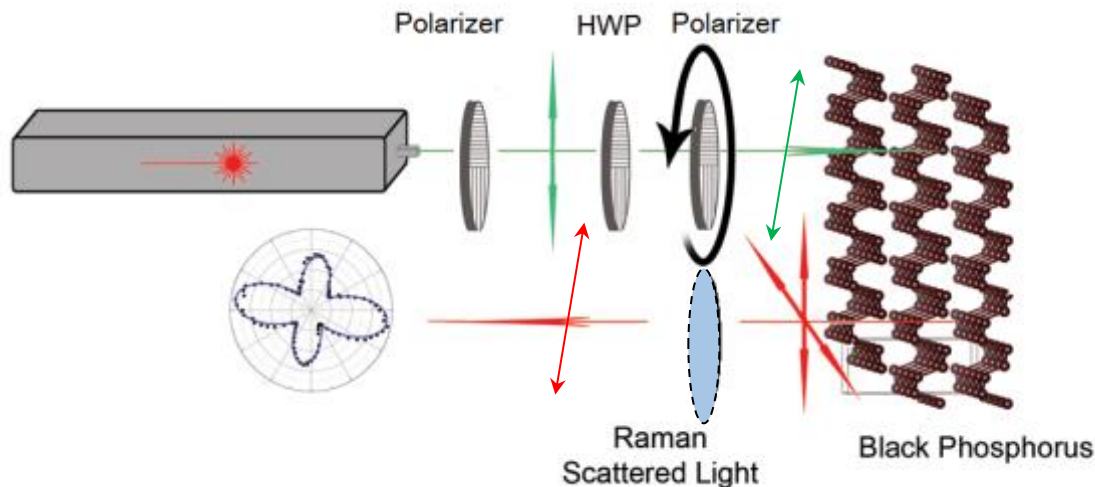


Figure 5. in this figure, polaroid2 is only the one we use to control the direction. the angle between fast axis of the QWP and the polarization direction is  $45^\circ$ , which could create circle polarized light.

# Results

We rotated the polaroid2 from  $0^\circ$  to  $180^\circ$ , and gained the data of bp raman peak intensity. (Fig 6a) To indicate the circle polarized light is accurate, we do the same operation to the Si substrate. The data was shown in figure 6b.

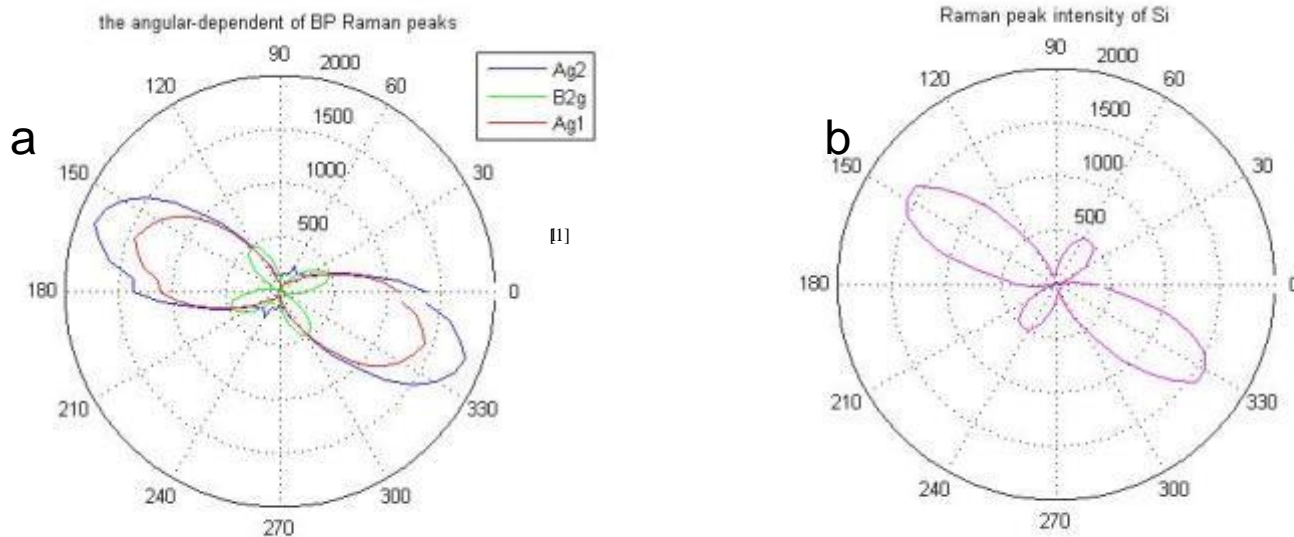


Figure 6a shows the angular-dependence of the blackphosphorus layers. As we have mentioned, this is the parallel configuration data. As the Raman tensor theory can predict, the parallel configuration of Ag1 and Ag2 changes following the same law. Unfortunately, we gained the data of the Si (Fig. 6b), which shows our device did not perform well. Because the lattice plane of the Si is (1 0 0), which should result in four identical local maximum in a round. So it's too difficult to create a ideal polarized light this method should be reformed.

# Device setup -- second generation

Method II: As prof. Wang suggested, we finally use a polarizer and a half wave plate (HWP) to create the polarized light. HWP can change the direction of polarized light without changing the intensity. (Fig 7)

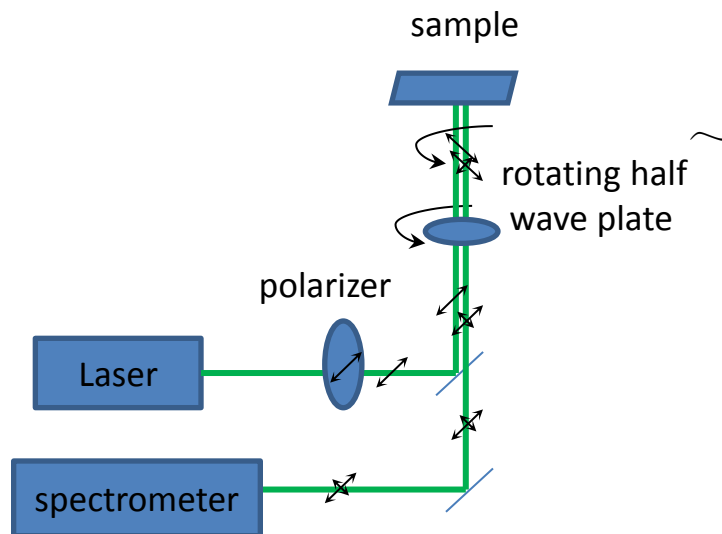


Figure 7. The device we finally used. The linearly polarized light changes its direction for  $2\theta$  as the HWP rotates  $\theta$ . In case the polarization light in other direction would appear, we put the polarizer along the horizontal direction. And we rotate the HWP with a rotation stage driven by a computer program.

# Results

We carried out this experiment, and get a group of data. We plot them as Fig 8




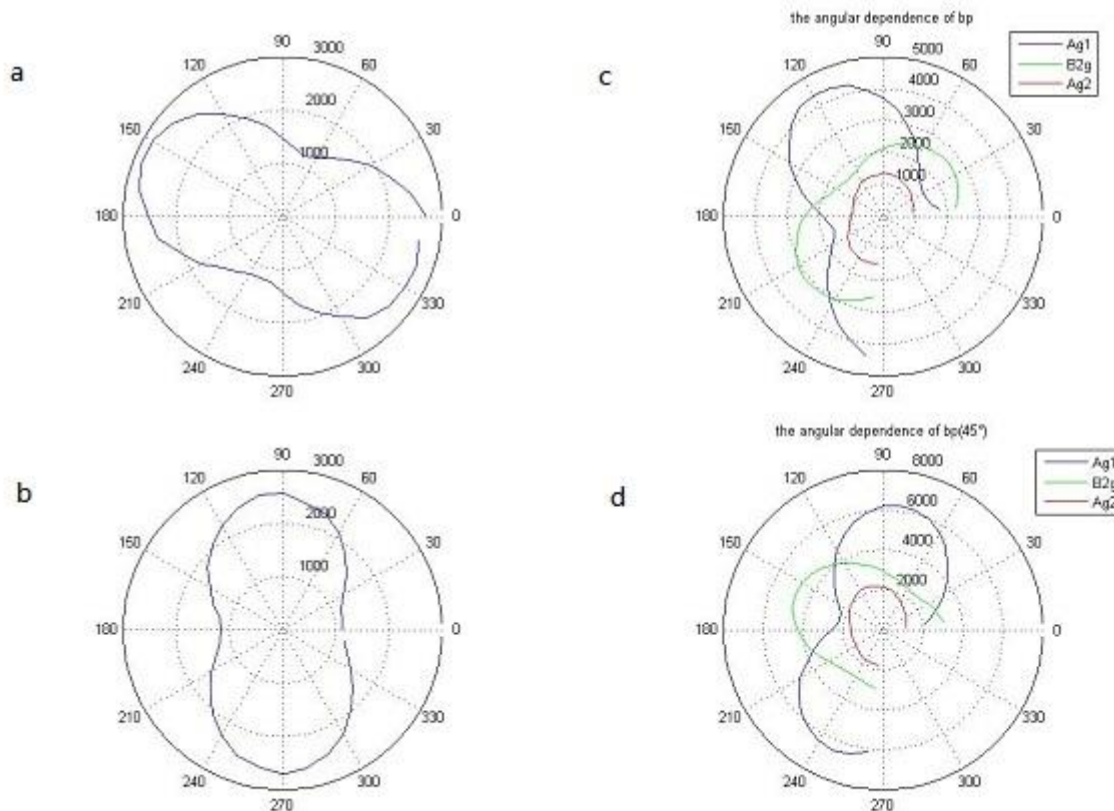


Figure 8.a&b shows the Si peak of this system, the angle this picture rotated is exactly that we rotated the sample, so the peak change has nothing to do with the light and device. so the data of bp is reliable. c&d shows the angular dependence of the bp, that's what we want to explore. Clearly, the Ag2 peak shows the most strong anisotropy nature, we can use it to identify the crystalline orientation.

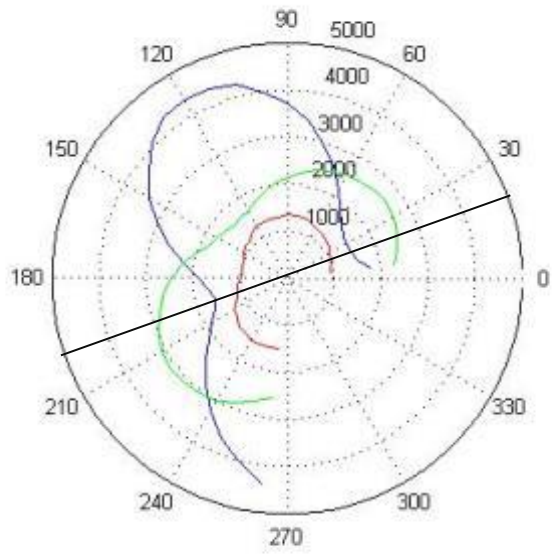

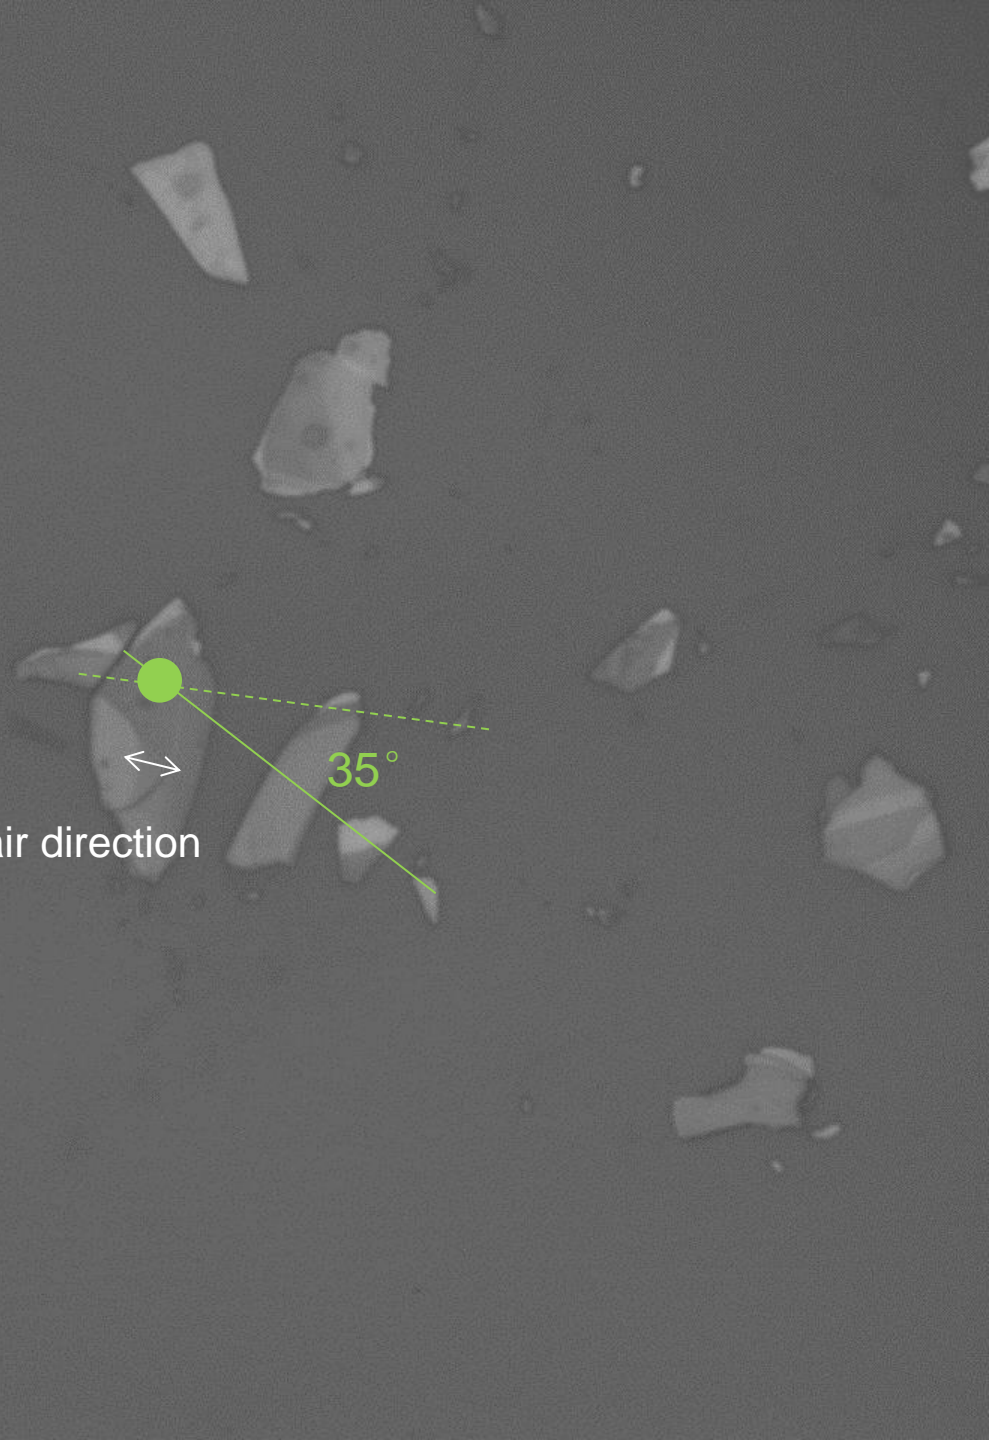

armchair direction

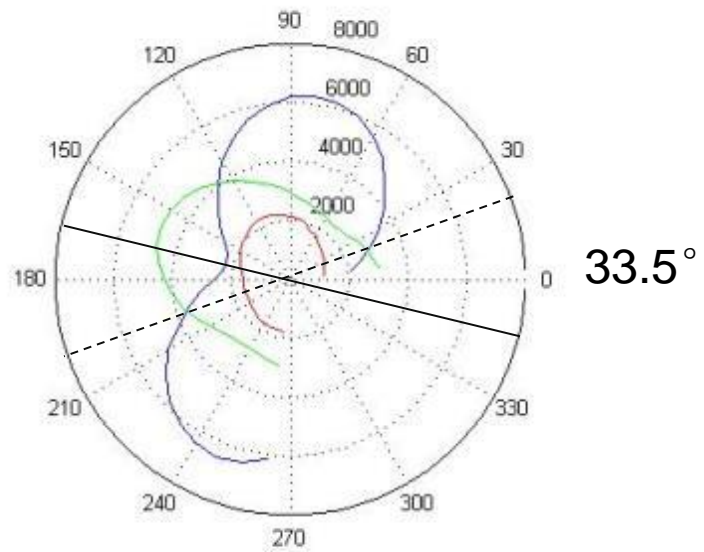

# Data fitting

- Theories of Raman scattering gives the following result about the intensity versus the direction of polarization of the incident beam

$$S_{A_g^2} = \frac{1}{2}(a^2 + c^2) + \frac{1}{2}(c^2 - a^2)\cos(2\theta)$$
$$S_{B_{2g}} = f^2$$

- where  $a$ ,  $c$  and  $f$  are all Raman tensor elements. And  $\theta$  is the angle between incident beam polarization direction and zigzag direction (10.1021/acsnano.5b00698)
- $A_g^2$  peak maximum  $\leftrightarrow$  polarization along zigzag direction
- $A_g^2$  peak minimum  $\leftrightarrow$  polarization along armchair direction



# Data fitting

- We fitted the data of  $A_g^2$  peak with *sum of sin* mode in matlab
  - $y = 4342 + 2075 \sin(2.17 x - 1.52)$
- The parameter before  $x$  is supposed to be 2. The discrepancy may due to imprecise of the rotation stage

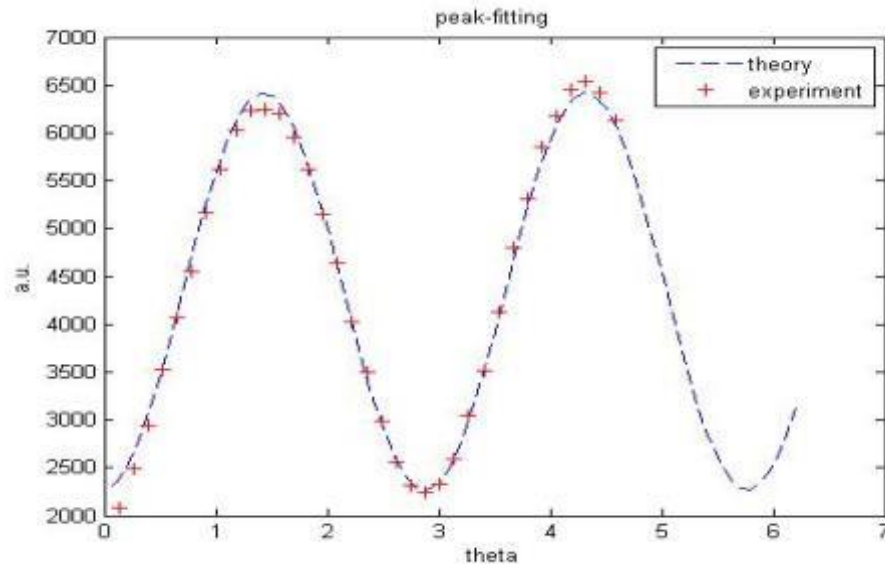


Figure 6. the red "+" is the experimental data of  $Ag_2$  peak, the dotted line is the fitted curve, Data fitting gives  $y = 4342 + 2075 \sin(2.17 x - 1.52)$  the phase difference and the angular velocity.

# Conclusion and unsolved problems

- At the very beginning the incident beam is polarized horizontally in the vision field. As the stage rotates, the polarization direction rotates anticlockwise.
- The  $A_g^2$  peak reaches the maximum at  $x = 0.700 \text{ rad} = 40.1^\circ$  that is the zigzag direction.
- The precision of the system is limited by the rotation stage


## 3.0 AG-PR100 Rotation Stage



### 3.1 Specifications




|   |   |
|---|---|
| Optics diameter                           | 1.0 in (25.4 mm)  |
| Max. optics thickness                     | 0.40 in. (10 mm)  |
| Travel range                              | 360° continuous   |
| Minimum incremental motion <sup>(1)</sup> | 5 $\mu$ rad (1 arcsec)  |
| Maximum speed                             | 2 °/s   |
| Wobble                                    | 100 $\mu$ rad   |
| Limits                                    | None  |
| Weight                                    | 135 g   |
| Graduation                                | 2°  |
| Cable                                     | 1.2 m length, 4-wire mini-Din connector.<br>Can extend cable length using AG-MD4-1.5 extension cable. |

<sup>(1)</sup> The step size for forward and backward direction is adjustable. With default settings, the step size for the forward direction varies from the step size for the backward direction and may be larger than 5  $\mu$ rad. Individual steps are not 100% repeatable.



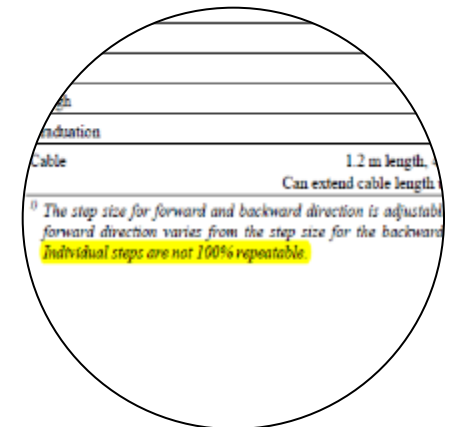


# Supplementary Information

- To ensure that the intensity of the beam remains unchanged when the HWP is rotating, we took the angle-resolved Raman spectrum of graphene and the silicon substrate.
- The result indicated that for material with high symmetry like graphene, the Raman peaks show little anisotropic characters.
- For Silicon, when the incident beam is perpendicular to the  $[1,0,0]$  face

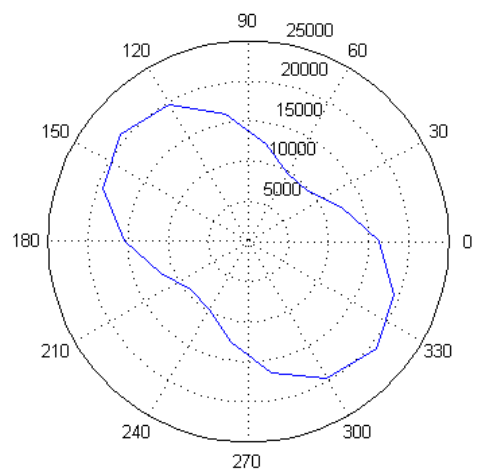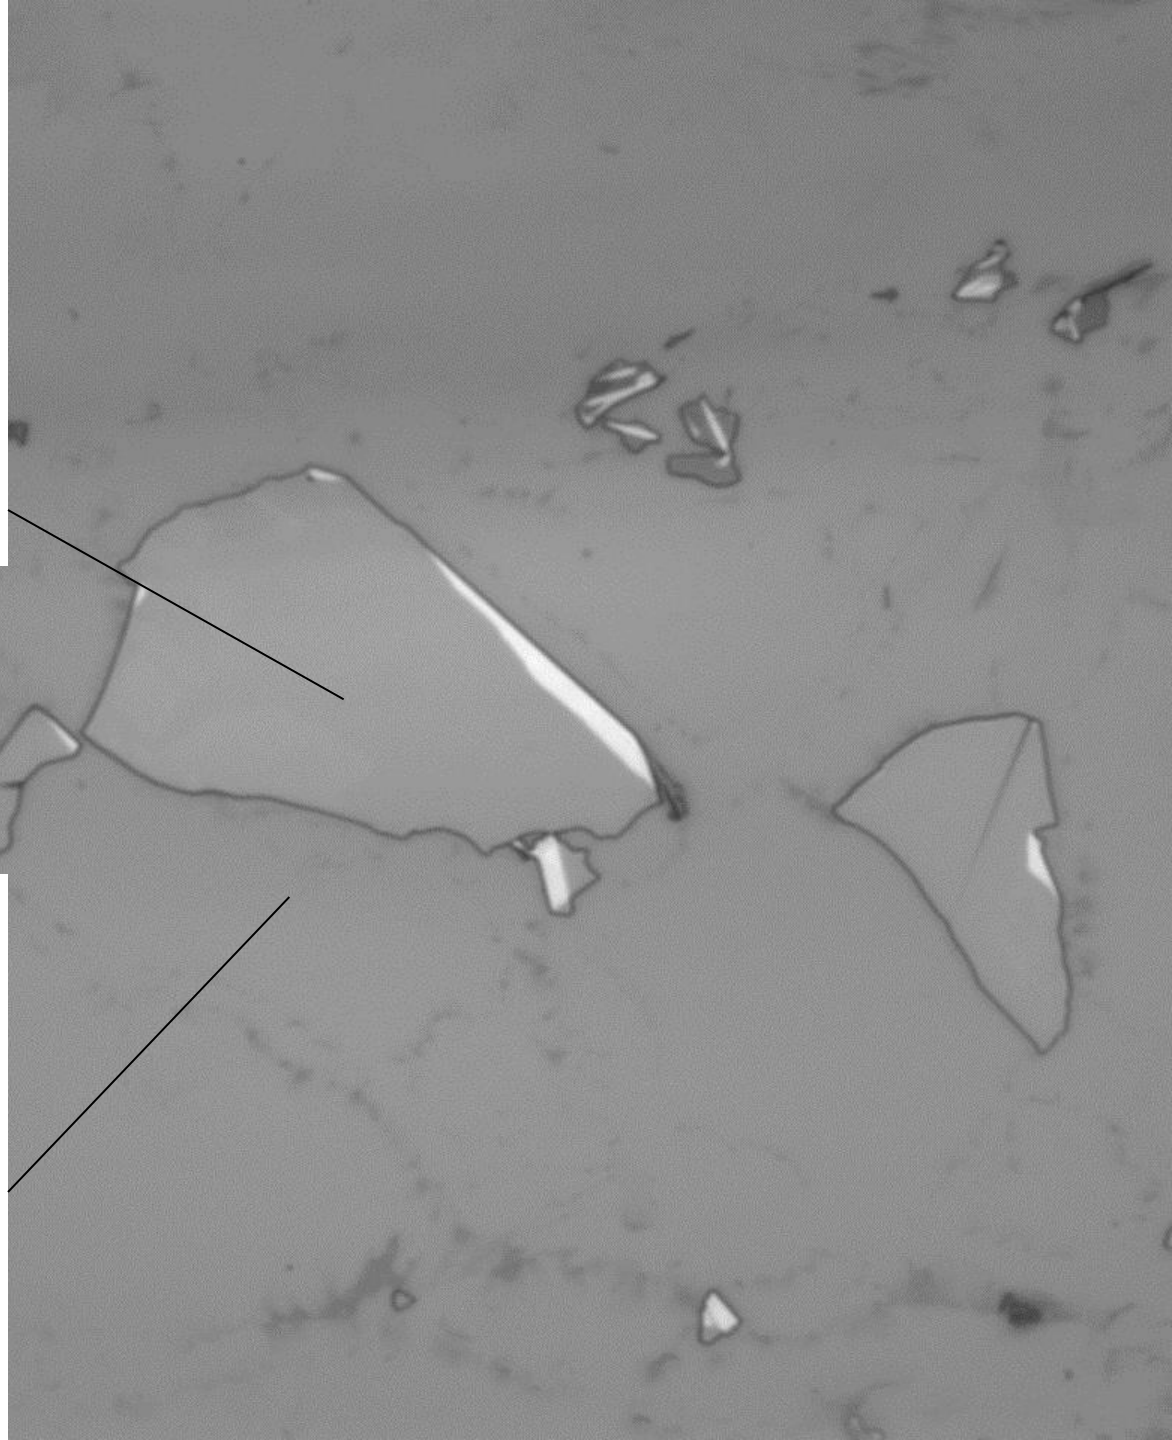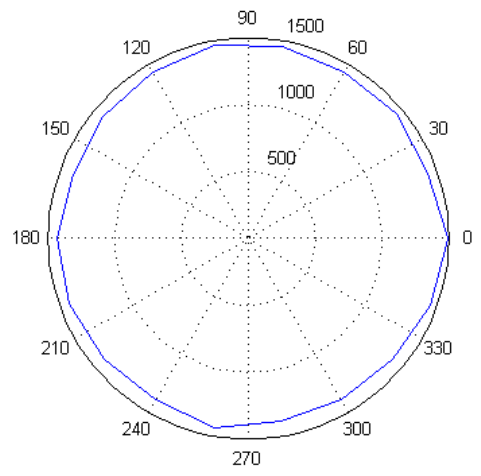




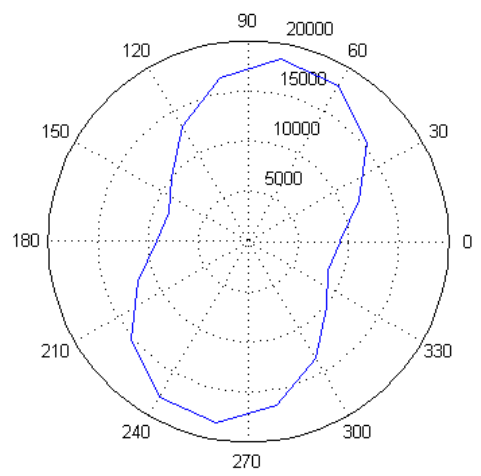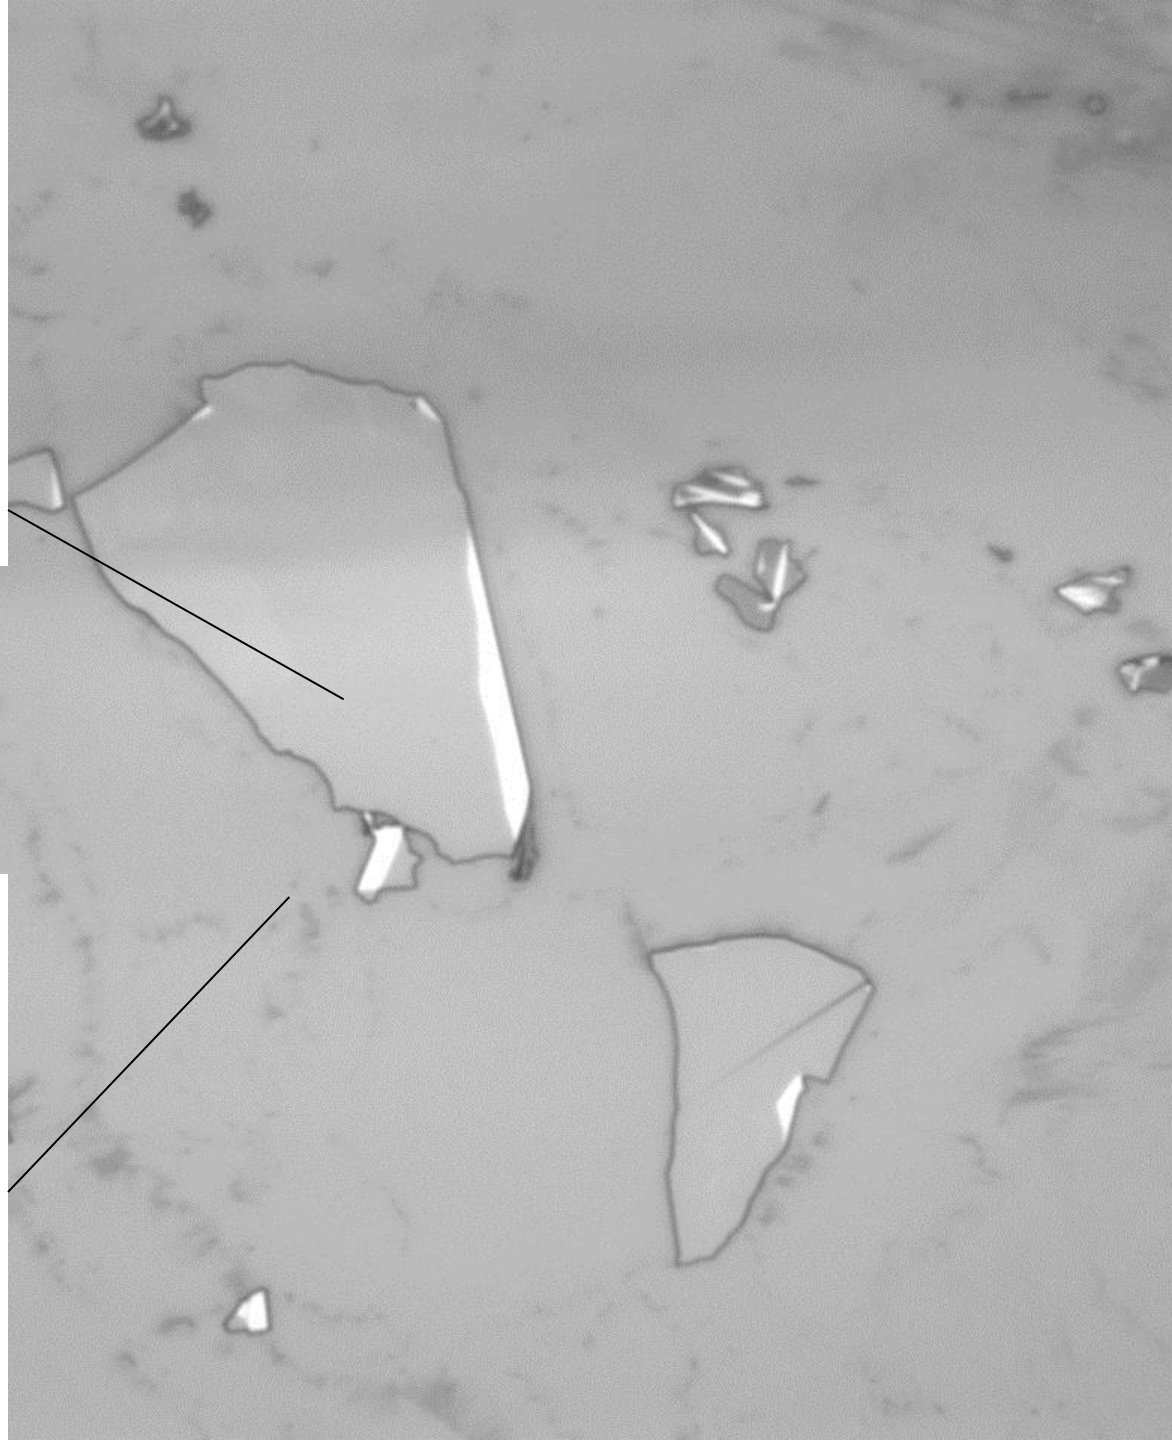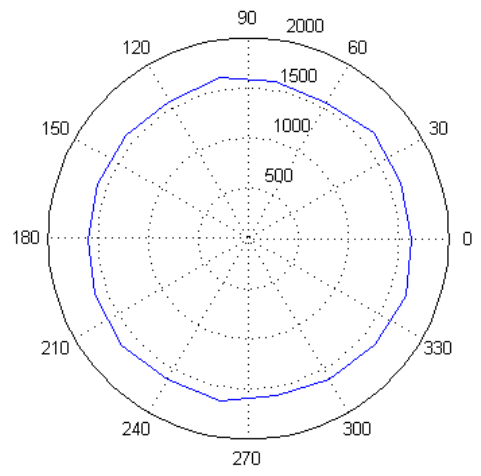




## II. Utilizing the anisotropic transmission rate and reflection rate of IR


# Theory

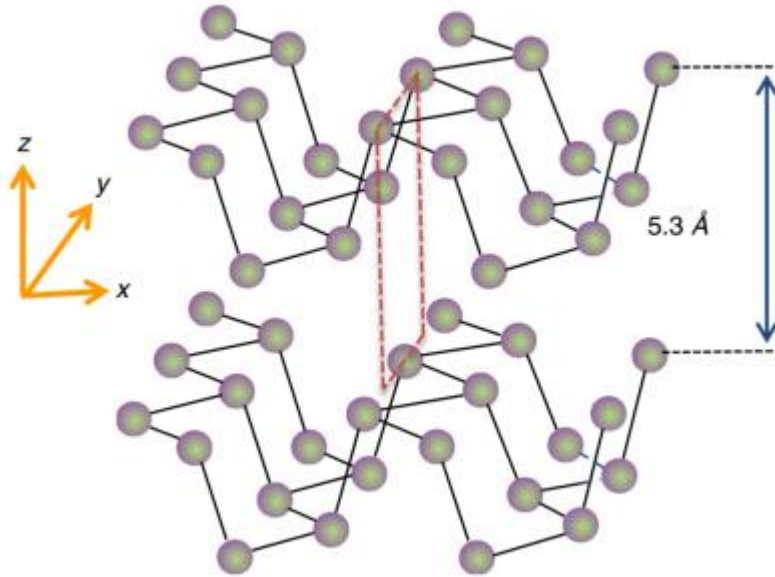

The anisotropy in optical conductivity arises from the directional dependence of the interband transition strength in the anisotropic BP bands.

Optical conductivity of BP peaks at the x-direction at the band edge.

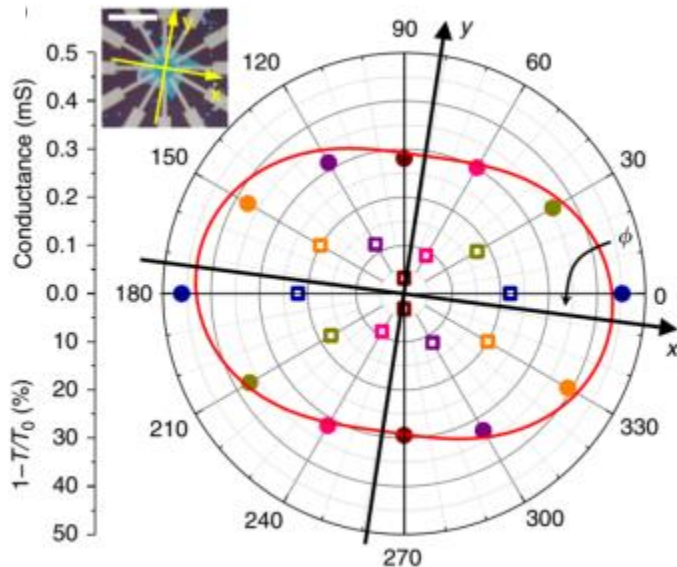



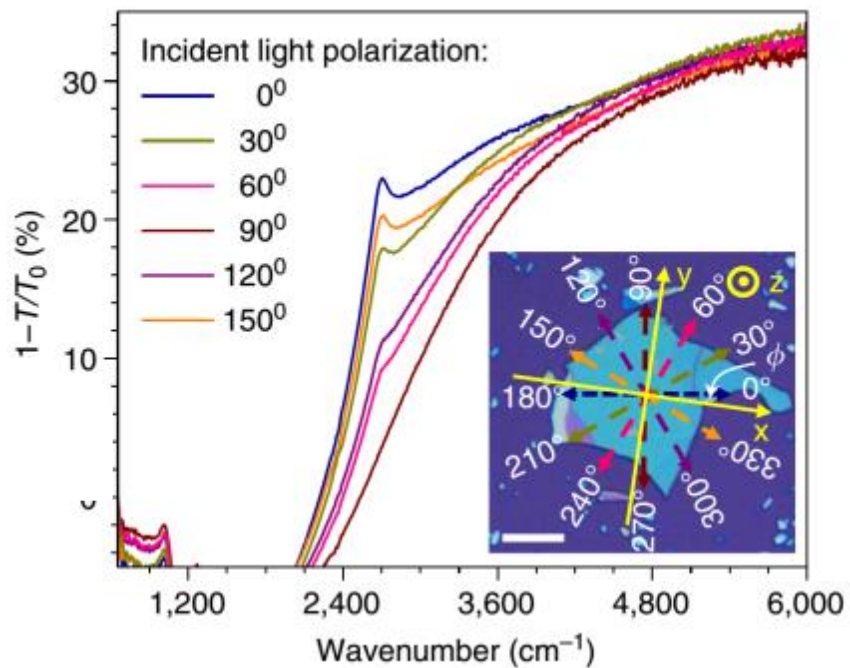




- For all polarizations, the extinction shows a sharp increase at around 2400( $\text{cm}^{-1}$ ), indicating a band gap of around 0.3eV.

## Reference:

*'Rediscovering black phosphorus as an anisotropic layered material for optoelectronics and electronics'* Fengnian Xia<sup>1,\*</sup>, Han Wang<sup>2,\*</sup> & Yichen Jia<sup>1</sup>



# transmission

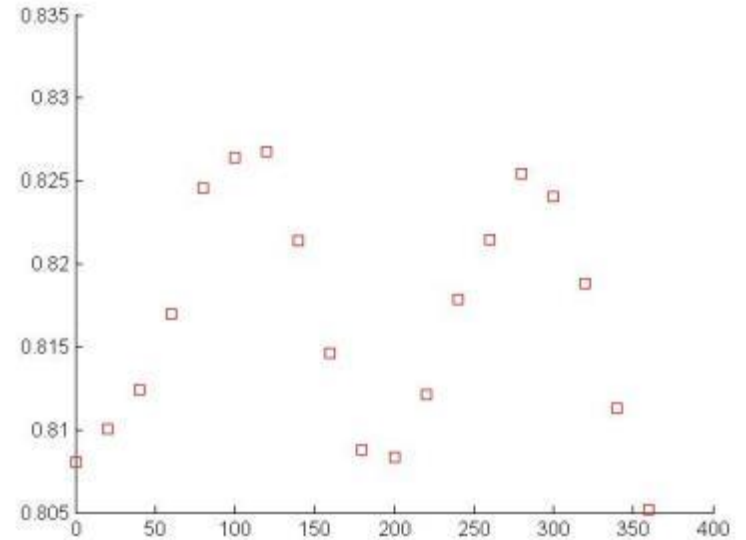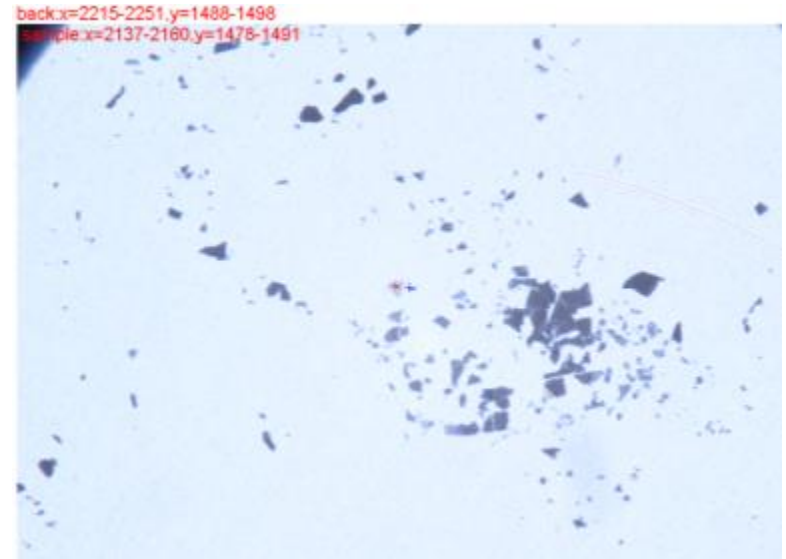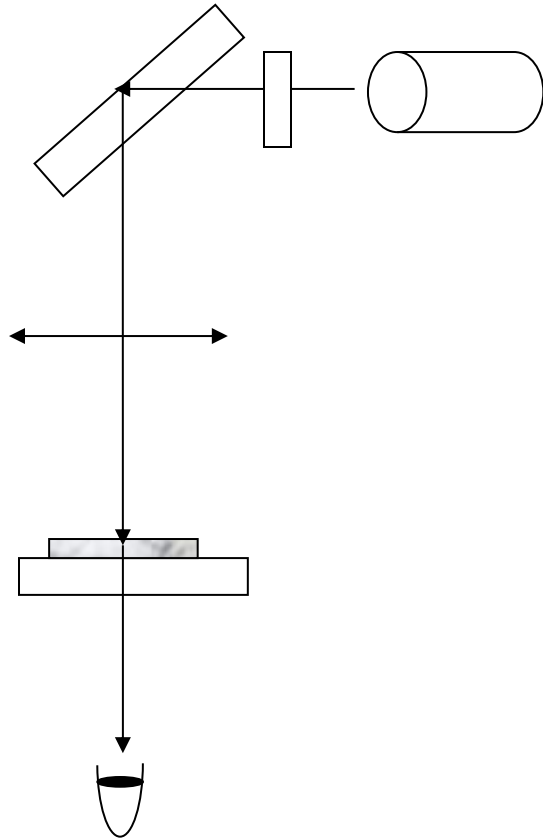

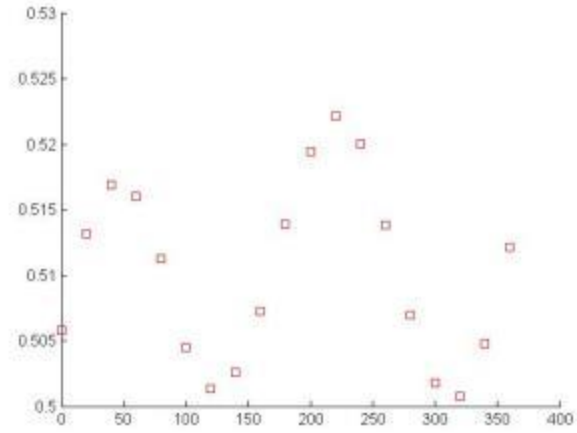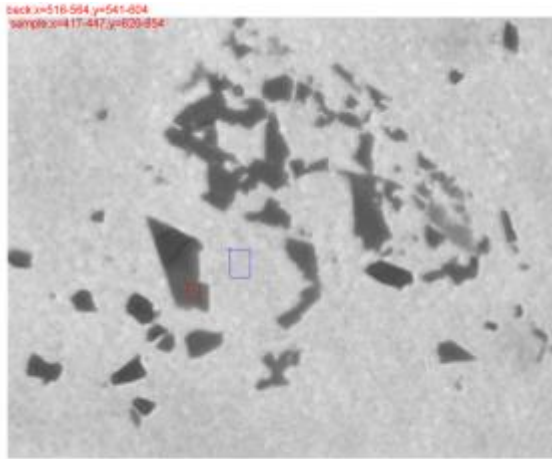


70,125,220,310

After rotation of 33 degree

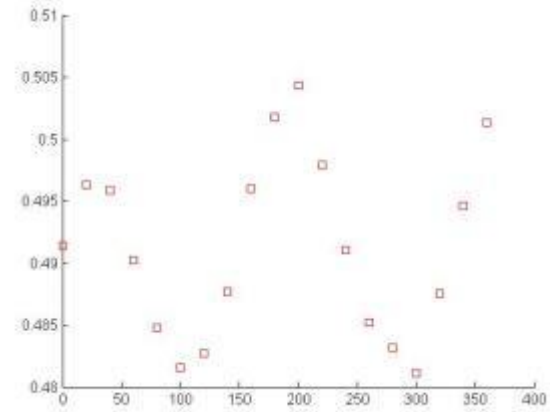
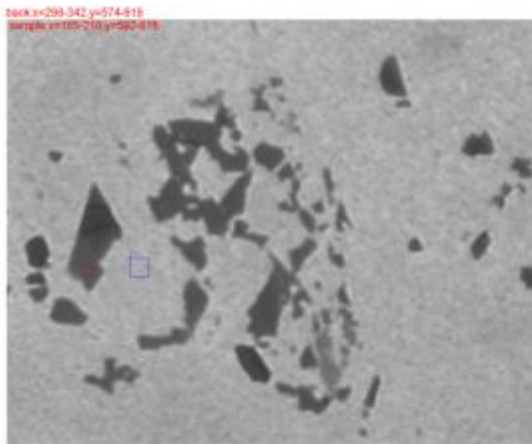


50,105,190,290


# reflection

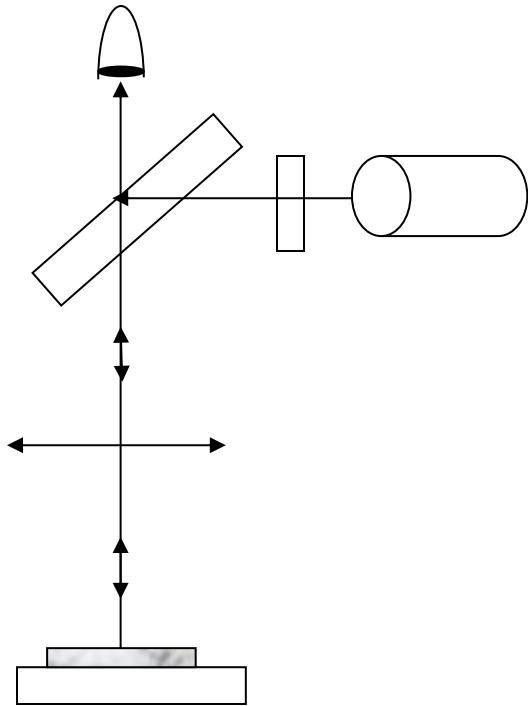


back:x=1019-1040 y=139-175  
sample:x=820-860 y=744-827

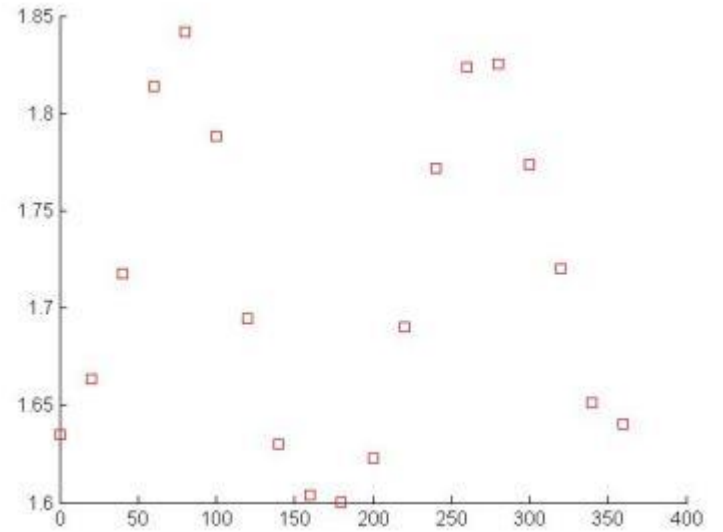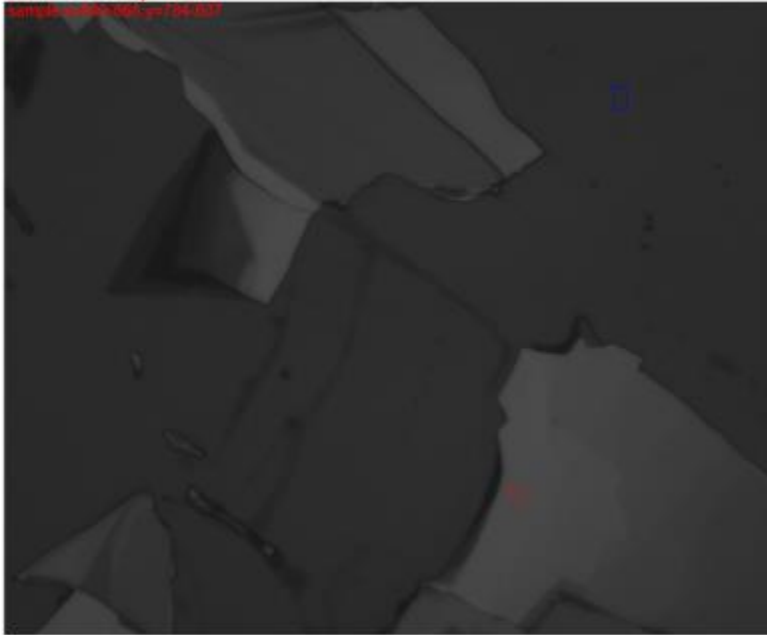

Contrast


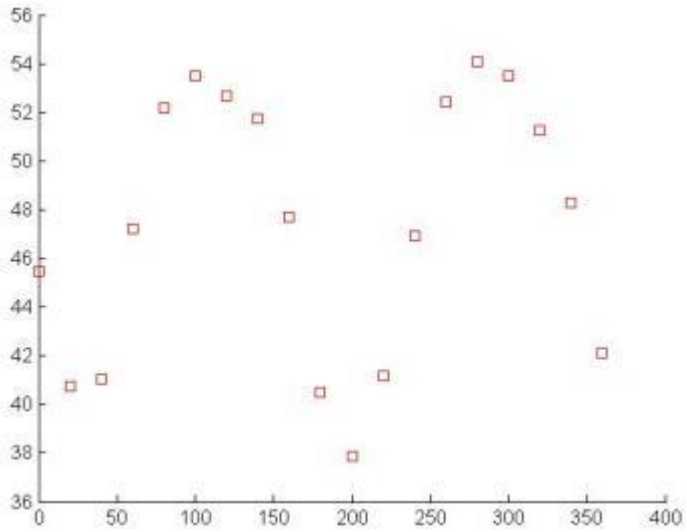


Background

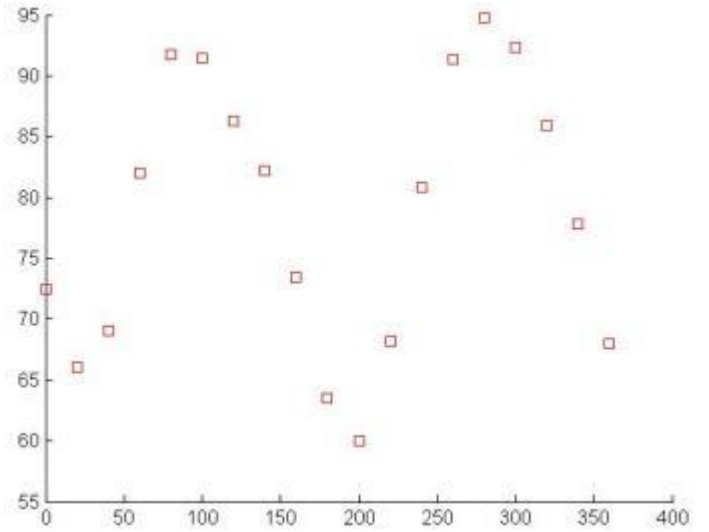


Sample


back x=857-871,y=466-478  
sample x=61-85,y=466-478

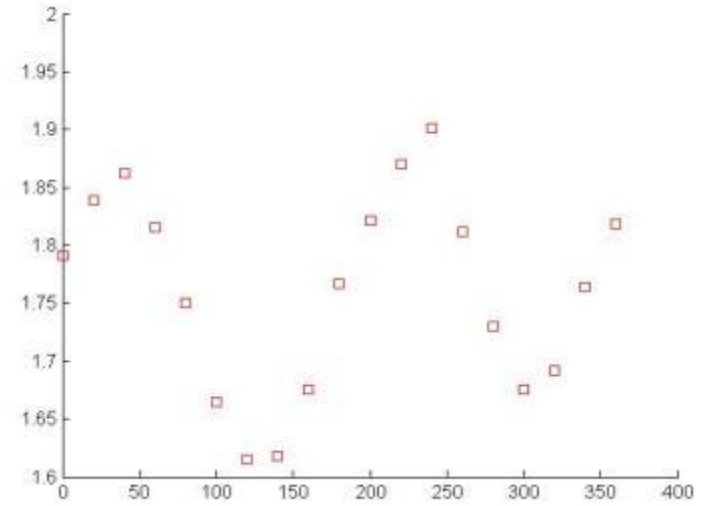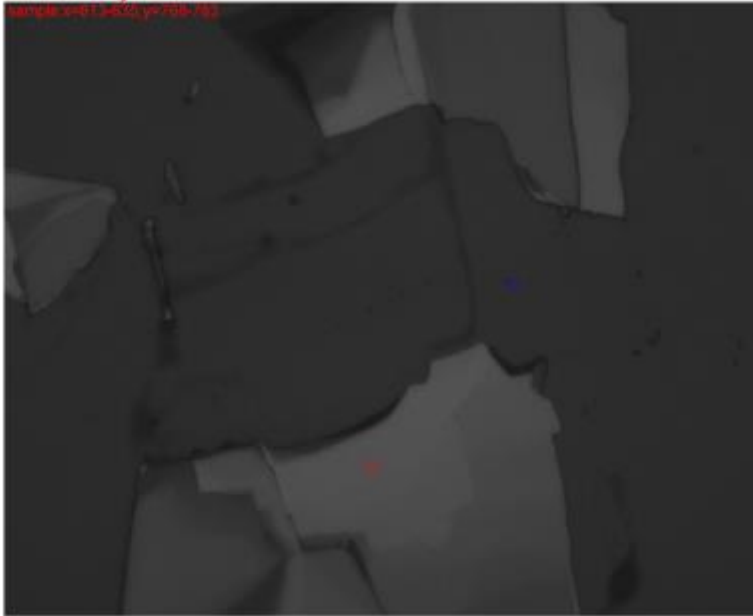

Contrast

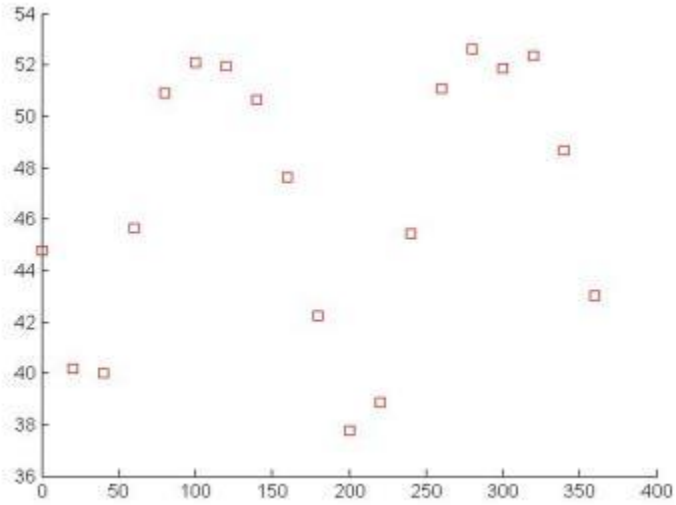


Background

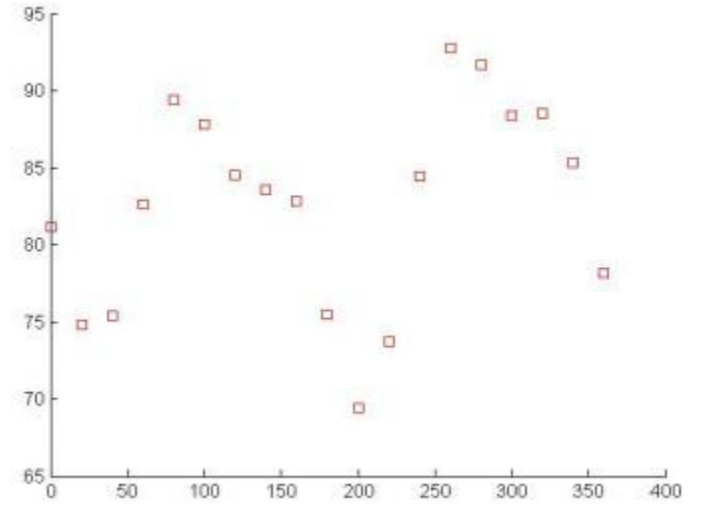

Sample



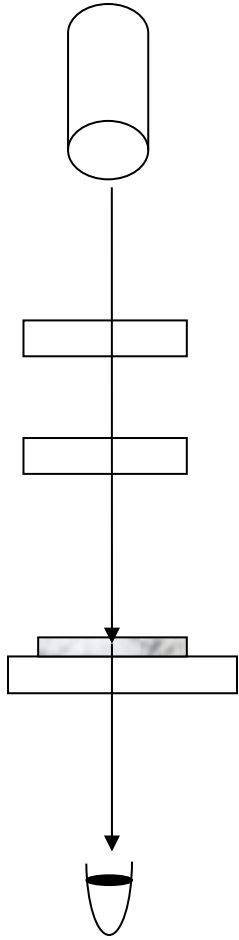

**THANK YOU**